

Study of the Phase Diagram and the T_c Pressure Dependence in the $HgBa_2CuO_{4-\delta}$ Superconductors

E. V.L. de Mello and C. Acha
*Centre National de la Recherche Scientifique,
 Centre de Recherche sur les Très Basses Températures
 Boite Postale 166, 38042 Grenoble-Cedex, France.*

We apply a method recently derived based on the extended Hubbard Hamiltonian to obtain the superconducting critical temperature dependence with carrier density of $HgBa_2CuO_{4-\delta}$. We show that this approach can be used to study the effects of pressure and reproduces for the first time the experimental data for the whole doping regime and their high and low pressure dependence.

One of the effects of the pressure which is generally accepted is an increase of the carrier concentration on the CuO_2 planes transferred from the reservoir layers. Such pressure induced charge transfer (PICT) has been confirmed by Hall effect and thermoelectric power measurements in several compounds [1]. Therefore this effect was largely explored to account for the quantitative relation between T_c and the pressure P and gave origin to several models [3–5]. Some of these models also invoked that several HTSs have a T_c versus carrier density n (per CuO_2) diagram which satisfies a phenomenological universal parabolic curve, i.e., $T_c = T_c^{max}[1 - \eta(n - n_{op})^2]$ where n_{op} is the optimum n . Following along these lines we can write $T_c = T_c(n, P)$ and easily derive a expansion in powers of P , namely

$$T_c(n, P) = T_c(n, 0) + \alpha_1(n)P + \alpha_2(n)P^2 \quad (1)$$

where the coefficients are,

$$\alpha_1(n) = \partial T_c(n)/\partial P - 2\eta T_c^{max}(n - n_{op})\partial n/\partial P \quad (2)$$

in which the first term is known as the intrinsic term and $\alpha_2(n) = -\eta T_c^{max}(\partial n/\partial P)^2$. This simple method was very successful in describing the data in the vicinity of n_{op} [4] but fails to describe more recently set of data with a large variation of n values from underdoped to overdoped regime [1,6]. Furthermore this phenomenological approach does not give any indication of the physical origin of the intrinsic term.

We propose in this work some new ideas to interpret the effects of pressure. We apply a recently introduced approach [8] based on a BCS type mean field analysis which uses the extended Hubbard Hamiltonian (t-U-V) on a square lattice (of lattice parameter a).

In connection with this method we are led to propose that the effects of pressure are two-fold: (i)- The well accepted PICT; (ii)- The relation $2\Delta_0 = \gamma K_B T_c^{max}$

($\gamma = 3.5$ for weakly BCS and $\gamma \approx 4.3$ for the method mentioned above) suggests a very definite effect of the pressure on Δ_0 . This is equivalent to say that the structural modifications due to the applied pressure cause a variation on the attractive potential V (which is the most influential parameter on the value of Δ_0). In fact the real effect of the structural changes can only be estimate by electronic band calculations [1,2,7], but they are not adequate to be performed in the presence of the strong correlations of the t-U-V Hamiltonian.

The above assumptions can be simple written as $T_c = T_c(n, \Delta_0)$ and $\Delta_0 = \Delta_0(P)$. On Fig.1 we plot two curves to study how T_c changes with Δ_0 . If we now perform an expansion of T_c in terms of P , we obtain terms up to the third order and each coefficient is given by

$$\alpha_Z = \left(\frac{\partial}{\partial \Delta_0} \frac{\partial \Delta_0}{\partial P} + \frac{\partial}{\partial n} \frac{\partial n}{\partial P} \right)^Z T_c(n, \Delta_0) \quad (3)$$

where $Z = 0, 1, 2$ and 3 is the order of the corresponding coefficient. We can derive simple analytical expressions for each coefficient in an approximate way, using the universal parabolic fitting and with $T_c^{max}(P) = 2\Delta_0(P)/\gamma$ which explicits the T_c dependency on P (assumption ii). This procedure gives an intrinsic term which is radically different than that derived on the basis of the PICT alone as well as a new third order term.

To illustrate the entire method we will apply it to the mercury system. The mercury family of compounds represents a real challenge to any theory for the following reasons: (a)- The highest transition temperatures obtained up to date have been measured on Hg1223 at 25-30 GPa [9–11] reaching values up to 164K. (b)-The set of data for the underdoped and overdoped regime for the $HgBa_2CuO_{4-\delta}$ (Hg1201) could not be interpreted [6] by the simple PICT models. (c)- The largest pressure effect on T_c with a change of almost 50K over a span of 20 GPa has been recently measured [12] in the Hg2212.

We apply now the above general procedure to the low pressure results of Cao et al [6] for the Hg1201. Thus to compare with their data we fix the linear term at $n_{op} = 0.16$, $\alpha_1 = 1.85\text{K/GPa}$ (which is equal to the intrinsic term and from this we determine $\partial \Delta_0/\partial P$) and at $n = 0.06$ we take $\alpha_1 = 2.6\text{K/GPa}$ (the intrinsic term is then 0.9K/GPa and the charge transfer is equal 1.7K/GPa what gives $\partial n/\partial P = 1.8 \times 10^{-3}$). Thus the value that we obtain to $\partial n/\partial P$ is very close to other calculations [3,5,12] and in this way all the coefficients of Eq. (3) are determined. Far from n_{op} the charge trans-

fer term dominates over the intrinsic one and the linear term decreases up to -1.0K/GPa (at $n=0.26$) in the overdoped region. Our results for all densities n are in excellent agreement with the experimental data in both the underdoped and overdoped region, as shown on Figs.1a and 1b.

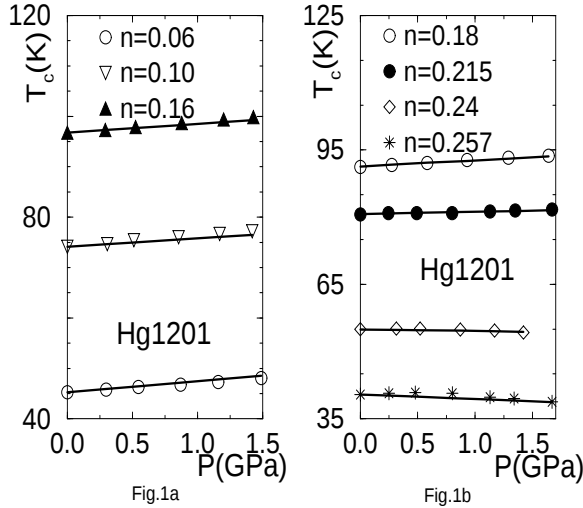


FIG. 1. a) The lines are our calculations for the underdoped region in comparison of the experimental points of Ref.6. b) The same our calculations for the overdoped region in comparison of the experimental points of Ref.6.

In Fig.2 we show the results for the high pressures measurements for the three family of compounds of mercury [11] at n_{op} . At the high pressures the quadratic and the cubic terms in the pressure expansion become important (for $P > 20$ GPa) and the agreement with the data is also remarkable. It is very interesting that the values obtained above at the low pressures yielded results with the maxima around 30GPa which is the value of highest T_c for a HTSs [11]. For the first time a simple theory is capable to describe successfully all this ensemble of data.

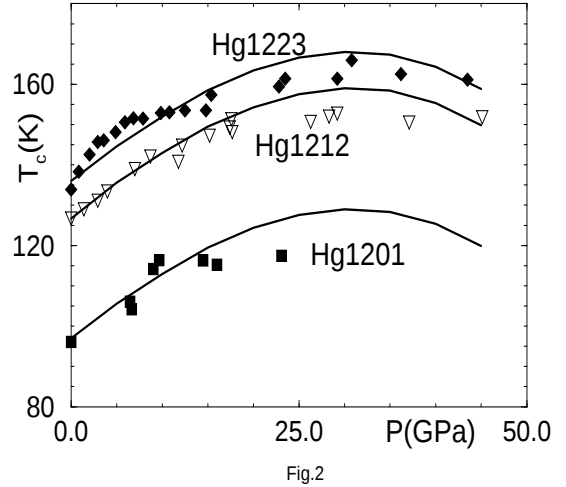


FIG. 2. The high pressures data of Ref.11 and our calculations (the continuous lines).

Thus, we conclude pointing out that our novel calculations (based on a BCS type mean field with the extended Hubbard Hamiltonian) demonstrate to be highly successful to describe the effects of the pressure with just two simple assumptions. The PICT which is well accepted and that of the pressure induced variation of the superconductor gap which was introduced, to our knowledge, in this work. We hope that this assumption can be confirmed in the future by in situ experiments like specific heat and tunneling measurements. As this work came to completion, we learnt about the work of Angiella et al [13] which also uses the extended Hubbard model within a BCS type approach. Furthermore they estimate the effects of the pressure on the attractive potential V which goes along with the lines of our assumption over Δ_0 . They also obtained very good results for the effects of pressure in the Bi2212 family, given more support to the BCS mean field calculations with the extended Hubbard as a model for the the physics of the charge carriers in the HTSs.

-
- [1] H.Takahashi and N.Mori, in "Studies of High Temperature Superconductors", vol.16, edited by A.V.Narlikar,(Nova Science, N.Y.,1996).
 - [2] J.S.Schilling and S.Klotz, in "Physical Properties of High Temperature Superconductors",edited by D.M.Ginsberg, VolIII, (World Scientific, Singapore 1992).
 - [3] C.C. Almasan, Phys. Rev. Lett. **69**,680(1992).
 - [4] J.J. Neumeier and H.A. Zimmermann, Phys. Rev. **B47**, 8385,(1993).
 - [5] R.P. Gupta and M. Gupta, Phys. Rev.**B51** 11760(1995).
 - [6] Y.Cao, Q.Xiong, Y.Y.Xue and W.Chu, Phys. Rev **B52**,

6854(1995).

- [7] D.L. Novikov et al, Physica **C222**, 38 (1994).
- [8] E.V.L.de Mello, Physica **C259**, 109(1996).
- [9] C.W.Chu et al, Nature 365, 323(1993).
- [10] M. Nunez-Regueiro et al , Science 262, 97(1993).
- [11] L.Gao et al, Phys.Rev. **B50**, 4260(1994).
- [12] C. Acha et al, submitted to the Solid State Comm..
- [13] G.G.N. Angiella et al Phys. Rev.B, december of 1996.